

Agglomerated Welding Flux BF 3

Flux type: Aluminate-Basic

Classification: ISO 14174 – **S A AB 1 67 AC H5 ***
(EN 760 – **SA AB 1 67 AC H5**)

Characteristics:

BF 3 is an agglomerated aluminate-basic flux with high current-carrying capacity, specially designed for the welding of wind towers by tandem arc. It is also suitable for joint welding of unalloyed and low alloy structural steels, pipe steels, boiler steels and fine grain steels. The flux is suitable for single and multilayer welding of longitudinal, circumferential and fillet welds. It can be used for single, tandem, twin and multi wire welding systems. Excellent slag removal in narrow groove welds of thick wall sections. Typical characteristic of this flux is a medium Mn and Si pick up as well as very low diffusible hydrogen level. It is suitable for both AC and DC welding.


Application:

Joint welding of non-alloy and low alloy structural steels acc. to. EN 10025. Fine-grain structural steels with $YS < 420$ MPa and boiler steels such as P265GH (H II) and 16Mo3/A335 grade 91

Characteristic chemical Constituents:

SiO ₂ + TiO ₂	Al ₂ O ₃ + MnO	CaO + MgO	CaF ₂
20 %	30 %	35 %	10 %
Basicity according to Boniszewski: ~1.9			

Metallurgical behaviour acc. to ISO 14174 type of current DC:

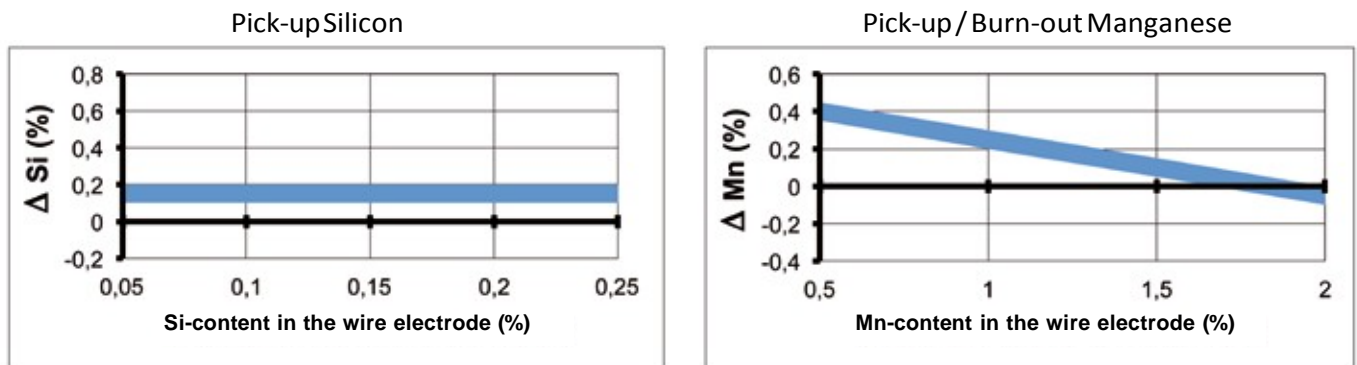

Flux density: 1.1 kg/dm³ (l)

Grain size acc. to ISO 14174: 2 – 20 (Tyler 8 x 48)

Current-carrying capacity: up to 1,500 A (DC or AC) using one wire

Packaging: 25 kg PE-bags or 500-1,250 kg Big Bags

Storage and redrying:

Unopened originally packed flux bags can be stored up to 1 year in dry storage rooms after date of delivery ex factory.

Redrying conditions specific to the flux: 200 ± 50 °C effective flux temperature.

*) Diffusible hydrogen content H5: determined in deposited metal acc. to the method described in ISO 3690 Type of current DC; redrying conditions 200 ± 50 °C

All-weld metal multiple pass classification of wire-flux combinations:

Wire electrode (ISO 14171-A ISO 24598-A)		Test assembly ISO 15792-1: type 1.3		AWS A5.17M/5.23M	AWS A5.17/5.23
ISO 14171-A	AWS A5.17/.2	ISO 14171-A			
BA-S1	EL12	ISO 14171-A	S 38 2 AB S1	F48A2-EL12	F7A0-EL12
BA-S2	EM12(K)	ISO 14171-A	S 42 4 AB S2	F48A4/P4-EM12(K)	F7A4/P4-EM12(K)
BA-S2Si	EM12K	ISO 14171-A	S 42 4 AB S2Si	F48A4/P4-EM12K	F7A4/P4-EM12K
BA-S3Si	EH12 K	ISO 14171-A	S 46 4 AB S3Si	F55A4/F49P4-EH12K	F8A5/F7P4-EH12K
BA-S2Mo	EA2	ISO 14171-A	S 46 4 AB S2Mo	F55A4/P4-EA2-A2	F8A4/P4-EA2-A2
BA-S2Ni2	ENi2	ISO 14171-A	S 50 5 AB S2Ni2	F62A5/F55P5-ENi2-Ni2	F9A6/F8P6-ENi2-Ni2

Two-run classification of wire-flux combinations:

Wire electrode (ISO 14171-A ISO 24598-A)		Two-run / ISO 15792-2: type 2.5		AWS A5.17M/5.23M	AWS A5.17/5.23
ISO 14171-A	AWS A5.17/.2	ISO 14171-A			
BA-S1	EL12	ISO 14171-A	S 2T 2 AB S1	F43TA2-EL12	F6TA0-EL12
BA-S2	EM12(K)	ISO 14171-A	S 3T 2 AB S2	F49TA2-EM12(K)	F7TA0-EM12(K)
BA-S2Si	EM12K	ISO 14171-A	S 3T 2 AB S2Si	F49TA2-EM12K	F7TA0-EM12K
BA-S3Si	EH12 K	ISO 14171-A	S 4T 3 AB S3Si	F55TA3-EH12K	F8TA2-EH12K
BA-S2Mo	EA2	ISO 14171-A	S 4T 2 AB S2Mo	F55TA2-EA2	F8TA2-EA2

Chemical composition of all-weld metal acc. to EN ISO 15792-1 and AWS A5.17/5.23: (characteristical values in wt. %)

Wire electrode		C	Si	Mn	Mo	Ni	Cr
BA-S1	EL12	0.05-0.08	0.2-0.4	0.9-1.3			
BA-S2	EM12(K)	0.05-0.08	0.2-0.4	1.4-1.8			
BA-S2Si	EM12K	0.05-0.08	0.2-0.5	1.4-1.8			
BA-S3Si	EH12K	0.05-0.08	0.2-0.5	1.6-2.0			
BA-S2Mo	EA2	0.04-0.08	0.2-0.4	1.3-1.7	0.5		
BA-S2Ni2	ENi2	0.05-0.08	0.2-0.4	1.1-1.5		2.0	

Mechanical properties of all-weld metal acc. to EN ISO 15792-1 and AWS A5.17/5.23: (characteristical values)

Wire electrode		Heat treatment	YS MPa	UTS MPa	Elong. %	Impact ISO-V (J)				
						± 0 °C +32 °F	-20 °C -4 °F	-40 °C -40 °F	-51 °C -60 °F	-73 °C -100 °F
BA-S1	EL12	AW	>400	>510	>24	>80	>47			
BA-S2	EM12(K)	AW	>420	>500	>22	>100	>70	>50		
BA-S2Si	EM12K	S*)	>400	>490	>22	>110	>80	>60		
		AW	>430	>520	>22	>100	>70	>50		
BA-S3Si	EH12K	S*)	>400	>490	>22	>110	>80	>60		
		AW	>470	>560	>22	>120	>90	>70		
BA-S2Mo	EA2	S*)	>400	>490	>22	>130	>100	>80		
		AW	>500	>570	>20	>100	>80	>47		
BA-S2Ni2	ENi2	S**)	>470	>570	>22	>110	>70	>47		
		AW	>540	>520	>22	>150	>120	>70	>47	
		S**)	>470	>550	>24	>150	>120	>100	>47	>60

Post Weld Heat Treatment: *) 580 °C / 1 h **) 620 °C / 15 h

Approvals:

 VdTUEV 1153 / TÜV Wien
 Deutsche Bahn

with wire electrodes:

 S2, S2Si, S2Mo, S2Ni2
 S2, S2Si, S2Mo